

## Research Article

# Statistical Analysis on Interlaminar Shear Strength of Nanosilica Addition with Woven Dharbai/Epoxy Hybrid Nanocomposites under Cryogenic Environment by Taguchi Technique

Muruganatham Ponnusamy <sup>1</sup>, L. Natrayan <sup>2</sup>, Pravin P. Patil,<sup>3</sup> G. Velmurugan,<sup>4</sup> and Yirga Terefe Keno <sup>5</sup>

<sup>1</sup>Deputy Registrar, Indian Institute of Information Technology, Kalyani, Webel IT Park, Kalyani, West Bengal 741235, India

<sup>2</sup>Department of Mechanical Engineering, Saveetha School of Engineering, SIMATS, Chennai, Tamil Nadu 602105, India

<sup>3</sup>Department of Mechanical Engineering, Graphic Era Deemed to be University, Bell Road, Clement Town, 248002 Dehradun, Uttarakhand, India

<sup>4</sup>Institute of Agricultural Engineering, Saveetha School of Engineering, SIMATS, 602 105, Chennai, Tamil Nadu, India

<sup>5</sup>Department of Civil Engineering, Ambo University, Ambo, Ethiopia

Correspondence should be addressed to Muruganatham Ponnusamy; mp@iiitkalyani.ac.in, L. Natrayan; natrayan.l.sse@saveetha.com, and Yirga Terefe Keno; yirga.terefe@ambou.edu.et

Received 8 May 2022; Revised 25 June 2022; Accepted 7 July 2022; Published 4 August 2022

Academic Editor: S.K. Khadheer Pasha

Copyright © 2022 Muruganatham Ponnusamy et al. This is an open access article distributed under the Creative Commons Attribution License, which permits unrestricted use, distribution, and reproduction in any medium, provided the original work is properly cited.

Biocomposites are becoming more popular due to their capacity to replace artificial materials at a lower cost while enhancing environmental responsibility. In contrast, biocomposites have poor mechanical and interface properties. This research is aimed at determining the interlaminar shear strength of composite materials reinforced with Dharbai fibre and nanosilicon powder. The composites were made using a hand lay-up method with the following conditions: (i) weight % of nanosilica filler, (ii) thickness of fibre mat, and (iii) cryogenic treatment period, each at three different levels, to meet the goals mentioned above. The composites were laminated using a traditional hand lay-up method, and their interlaminar shear strength was determined using the ASTM standard. According to a recent study, nanocomposites containing 4% nanoscale silicon and 300 grammes per square metre of woven Dharbai fibre showed the highest interlaminar shear strength after 15 minutes of cryogenic treatment. Fibre content increased the mechanical properties of pure epoxy in general. As the fibre and filler concentrations grew, more energy was required to break the fibre bundles between the matrix and its resin. According to the ANOVA, the cryogenic treatment was the most significant factor, contributing up to 59.58%, followed by woven Dharbai mate, contributing 22.11%, and nanosilicon at 18.30%. SEM is used to investigate the cracked composites' fractographic examination.

## 1. Introduction

Composite materials are getting popular and interested in developing materials and technology due to their better structural features and developing environmental issues such as climate change and contaminants. The physico-chemical characteristics of the fibre vary as the concentration of constituents such as lignocellulosic biomass, pectin,

lignin, and wax varies [1, 2]. Natural composite material is appropriate for various applications such as wrapping, construction, and automobile dashboards, due to inherent traits such as lighter density, cheap cost, great mechanical capabilities, and sufficient flexibility. Natural textiles, unlike synthetic materials, are recyclable, have no negative consequences, are easier to work with, and bear less weight [3, 4]. Furthermore, to improve the strength of mechanical

features of composite materials, cellulose fibres could be combined with manufactured fibres such as glass and carbon [5]. Dharbai (*Eragrostis cynosuroides*) is a commonly planted plant in both the southern and northern areas of India, and it produces a range of natural fibres. No attempt has yet been made to analyze this shrub for its fibre. As a result, this study is aimed at determining if Dharbai fibres can be used as a reinforcing material in epoxy matrix composites [6]. Due to variances in cellulose, hemicellulose, and lignin chemical components, natural fibres have varying potential. The fibre and matrix must interact and have affinities for the composite to have better properties.

Dharbai fibres are lignocellulosic fibres containing OH compounds that absorb water quickly and decrease the performance of natural composites, especially in terms of dimension stability [7]. Fresh untreated filaments must be pretreated with artificial chemicals to maximize effectiveness. It has eliminated extra cellulose, pectin, waxes, and hydrocarbons. It has critical because lignin, pectin, and lignocellulose function similarly, resulting in the bonding of microfibrils and the joining of neighbouring fibres to create a grouping. All this interferes with the proper dispersion of fibres within the polymer [8]. Sodium hydroxide (NaOH) is one such alkaline that is widely employed since it leaves no pectin remnants in the fibres following the alkali treatment. This also destroys the ethereal bonds by acidic breakage and eliminates them from the fibre surface. According to previous research, if unprocessed filaments are processed using 5% sodium hydroxide, the composites' load-carrying ability increases severalfold compared to composites generated from untreated fibres [9, 10]. The chemical treatment causes surface quality, facilitating binding between the fabrics and matrices. This can reduce the filamentous quantity by the oxidizing level, causing the crystalline phase of the finished good to be disrupted. It is advised that, following alkalization, the fibres be washed with purified water to remove any surplus caustic. After that, acidity processing with caustic soda is advised since investigations have shown that neutrality fibres possess excellent mechanical properties [11, 12].

One of the most trustworthy and recognized composites for producing models in the modern environment of materials and industrial engineering would be those built using nanoparticle-reinforced polymers [13]. Several studies have demonstrated that when nanocrystals are employed for reinforcing, the synthetic behavioural qualities increase more than the mechanical characteristics. Because of its remarkable electromagnetic, structural, and thermodynamic capabilities, nano-silicon oxide is another imperative element used for reinforcements [14, 15]. It has a solitary organism's width and a two-dimensional hexagonal design. It is widely employed in electrical and optical gadgets [16, 17]. Due to its durability, it has become an excellent filler in epoxy restorative materials. The presence of an oxide position in nanosilica material that functions as a powerful adhesive throughout the matrices is the primary explanation. The technique of blending nano-silicon oxide nanopellets with the polymer matrices is known as ultrasonic irradiation [18]. Cryogenic properties can improve the mechanical properties of fibre-reinforced composites. For example, materials used in aircraft

construction should tolerate extreme temperatures of up to 200°C.

Cryogenically treated composites and polymers have great strength, are more robust, and have increased stiffness and wear resistance. As a result, liquid nitrogen treatment of composites may become an essential part of ongoing research and development to improve natural composite material properties [19]. Taguchi parameter design helps streamline production processes and achieve high-quality goals while keeping costs low. The grey-based Taguchi approach was used to refine the parameters of several multi-response problems in the manufacturing system. Throughout this method, an orthogonal design of array (OA) is developed to assess a number of variables in reduced trials, and the S/N ratio is employed to assess the influence of noise components on target attributes. The S/N ratio consolidates the various data points inside an experimental, according to the research feature [20]. Three sorts of performance need to be considered when examining the S/N ratio: short the better, larger the better, and nominal the better.

The novel aspect of the current study can be highlighted by the fact that this is one of the first studies to investigate composites with woven Dharbai as reinforcement and nanosilica as filler material in epoxy resin under cryogenic conditions. It is envisaged that the results of this investigation could open up new application routes for natural fibre-based composites in extremely cold environments. The primary purpose of this research is to construct, test, and improve the mechanical properties of natural hybrid composites utilizing the following criteria: weight % of nanosilicon, the thickness of Dharbai fibre in grammes per square metre, and cryogenic treatment duration. Natural fibres were alkali-treated to improve adhesion and reduce moisture absorption, and their mechanical properties were examined and optimized using Taguchi procedures based on grey analysis. The nanosilicon filler-based composite materials were built using a simple hand lay-up procedure.

## 2. Experimental Works

*2.1. Materials.* This study made use of a Dharbai fibre mat. Jevanthi Enterprises in Chennai, Tamil Nadu, supplies these fibres. Normally, the Dharbai fibre mat was produced in the following manner. The Dharbai leaves are cut off using a knife and dried for three days in the shade. The fibres were then water retted for eight days and washed to remove any foreign pollutants that had developed during the retting process. The fibres were then dried for two days at room temperature to eliminate the moisture content. These dried length fibres were then used to make the Dharbai fibre mat. The resulting fibres were treated with an alkali solution prepared by adding NaOH grains in freshwater. In this study, nano-silicon oxide powder is an essential substance used to reinforce Dharbai fibre. Aside from these fibres and reinforcing components, the chemicals employed in this study include epoxy resin, polyamine hardener, and distilled water. The nanopowder and other chemicals were procured from Naga Chemicals, Chennai, Tamil Nadu, India. Figure 1



FIGURE 1: Photographic image of reinforcement, filler, and matrix materials.

shows the photographic images of reinforcement, filler, and matrix.

**2.2. Chemical Treatment of Natural Fibres.** Dharbai fibres are pretreated for 4 hours using filtered water and a 5% alkaline solution that repairs the filaments' cracked surfaces and improves the filament's surface morphology. The filaments are rinsed in acetic acid to remove excess base until the pH on litmus paper approaches [21].

**2.3. Sonication Process.** By sonication, different weight compositions of nanosilica were employed to prepare a solution. 100 ml methanol was combined with three grammes of silicon material. After this combination was generated, sonication was initiated and lasted 2 hours. To avoid evaporation, the water bath temperature was kept below 25 degrees Celsius throughout the procedure [22]. The sonicated solution then was combined with 250 millilitres of epoxy at 45°C to evaporate the methanol, and constant swirling was done using the incubation equipment to ensure good blending [23]. The metal rod was used to ensure a precise mix, and the slurry was then prepared to plunge the fibres in. The binding agent had been added, and the solution was well stirred for 3–4 minutes to get a nice smoothness and uniformity [24].

**2.4. Fabrication of Composites.** To begin, a steel mould with dimensions of 150 × 150 × 3 mm was fine-tuned. The Nanosilica powder and woven Dharbai fibre composites were created using a manual lay-up method. The produced matrix solution was strewn across the layers of fibres in the mould. After the fibre mats were thoroughly soaked with matrix combinations, the mould was affixed and dehydrated in the open air for one day [25]. For three restrictions, each with three stages, the L9 orthogonal array was chosen according to Taguchi's design, and nine composite plates were constructed for further exploration. Desiccators were utilized to prevent the hybrid composite samples from absorbing moisture [26]. The parameters and their values are listed in Table 1. Table 2 reveals the L9 orthogonal array along with the ILSS outcome.

**2.5. Cryogenic Treatment.** The cryogenic procedures were carried out in a temperature-controlled cryogenic chamber with programmed controls. A regulated cooling rate (3°C/min) was used to get the temperature down to 196°C. The produced samples were submerged in liquid N<sub>2</sub> at 77 K for

cryogenic treatment for 15 minutes, 30 minutes, and 40 minutes, respectively, according to the experimental design [27]. After the treatment, the composites were reheated at a continuous rate of 45°C/h to return to room temperature.

**2.6. Testing.** The fabricated composite samples were cut and rendered to the ASTM standard of D 2344 replicas with a dimension of 45 × 3 × 3 mm for interlaminar shear strength of the biobased nanocomposites.

**2.7. Fractographic Study.** SEM was utilized to conduct microscopic investigations into fractured composite samples [28]. The specimens were laved, dehydrated, and surface coated with 10 nm of gold before SEM clarity to increase the composites' electrical conductivity.

### 3. Taguchi Method

Taguchi's approach is the most effective for studying the relationship between various factors and executing fewer experimental plans, saving money and time. The mean result of quality features was used to perform the main effect evaluation at every variable range [29]. Furthermore, ANOVA was used to investigate the outcome and participation of each variable in the functional features [30].

**3.1. Taguchi Investigation and Their Results.** The Taguchi technique of the experimental process is a useful procedure for a logical explanation, research, and optimization of numerous process factors to achieve the desired effect. The investigative results are converted into an S/N ratio using this approach to discover the main constraints [31]. The S/N ratio characteristics were separated into three stages depending upon the conclusive reason for the major feature to be improved: (i) bigger the best, (ii) nominally the best, and (iii) smallest the best. The higher the S/N ratio, regardless of the performing feature group, the greater the performing feature [32]. As a result, the parameter's ideal level is the one with the largest S/N ratio. Flexural, tensile, and impact strengths were assessed throughout the composites testing using the greater principle [33]. As a result, S/N ratios of prominence characteristics (bigger is best) are explicitly expressed as [34]

$$S/Nratio = -10 \log_{10} \frac{1}{e} \sum_{a=i}^e \frac{1}{X_{ab}^2}. \quad (1)$$

TABLE 1: Constrains and their stages for composite.

Sl. No	Parameters	Symbols	Levels		
			L1	L2	L3
1	Silicon powder (wt.%)	A	2	4	6
2	Woven Dharbai thickness (gsm)	B	200	250	300
3	Cryogenic treatment (min)	C	15	30	45

TABLE 2: L9 orthogonal array and experimental results.

Trail No.	Nano silicon powder (wt.%) A	Woven Dharbai thickness (gsm) B	Cryogenic treatment (No.) C	ILSS outcome (MPa)	S/N ratio of ILSS
1	2	200	15	35.81	31.0801
2	2	250	30	36.16	31.1646
3	2	300	45	34.59	30.7790
4	4	200	30	37.37	31.4505
5	4	250	45	35.32	30.9604
6	4	300	15	34.32	30.7109
7	6	200	45	34.10	30.6551
8	6	250	15	34.92	30.8615
9	6	300	30	35.34	30.9653

TABLE 3: Average values of S/N ratio of nanocomposites.

Sl. No	Constraints	Level 1	Level 2	Level 3
1	Nano silicon powder (wt.%)	35.52	35.67	34.78
2	Woven Dharbai type (gsm)	34.75	35.46	35.76
3	Cryogenic treatment (min)	35.01	34.67	30.06

TABLE 4: Mean value of ILSS outcome.

Levels	Nanosilicon powder (wt.%)	Woven Dharbai type (gsm)	Cryogenic treatment (min)
1	35.52	35.76	35.02
2	35.67	35.47	36.29
3	34.79	34.75	34.67
Delta	0.88	1.01	1.62
Rank	3	2	1

TABLE 5: S/N values of ILSS outcome.

Levels	Nano silicon powder (wt.%)	Woven Dharbai type (gsm)	Cryogenic treatment (min)
1	31.01	31.06	30.88
2	31.04	31	31.19
3	30.83	30.82	30.80
Delta	0.21	0.24	0.40
Rank	3	2	1

Table 2 shows the results of interlaminar shear strength and associated S/N ratios. The mean data for S/N ratios may be computed using the data in Table 2. The following approach can be used to determine average values [35], for example, the parameters of the silicon nanofiller.

$$\text{Level 1} = \frac{35.81 + 36.16 + 34.59}{3} = 35.52, \quad (2)$$

$$\text{Level 2} = \frac{37.37 + 35.32 + 34.32}{3} = 35.67, \quad (3)$$

$$\text{Level 3} = \frac{34.10 + 34.92 + 35.34}{3} = 34.78. \quad (4)$$

The finest ideal parametric levels were discovered utilizing an ANOVA table, including stage 2 from silicon filler (4 wt.%), stage 1 from woven Dharbai type (200 gsm), and stage 2 from cryogenic treatment (30 min).

**3.2. ILSS Properties of Nanocomposites.** The interlaminar shear strength of the composite frame was tested using a universal testing machine (UTM) with a load cell limit of 5 kN. The sample was cut according to ASTM standard D-2344. A 45 mm long bar with a minimum thickness of (width = thickness) and square cross-segments was loaded under three-point bending [36]. The ILSS response of composites is used to detect if the material has shear behaviour between its layers. On composites, the ILSS test assesses

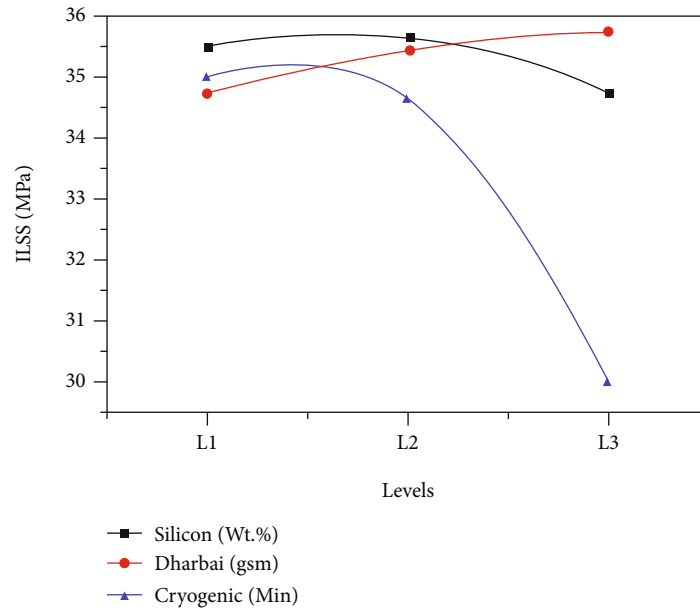


FIGURE 2: ILSS behaviour of nanocomposites under cryogenic environment.

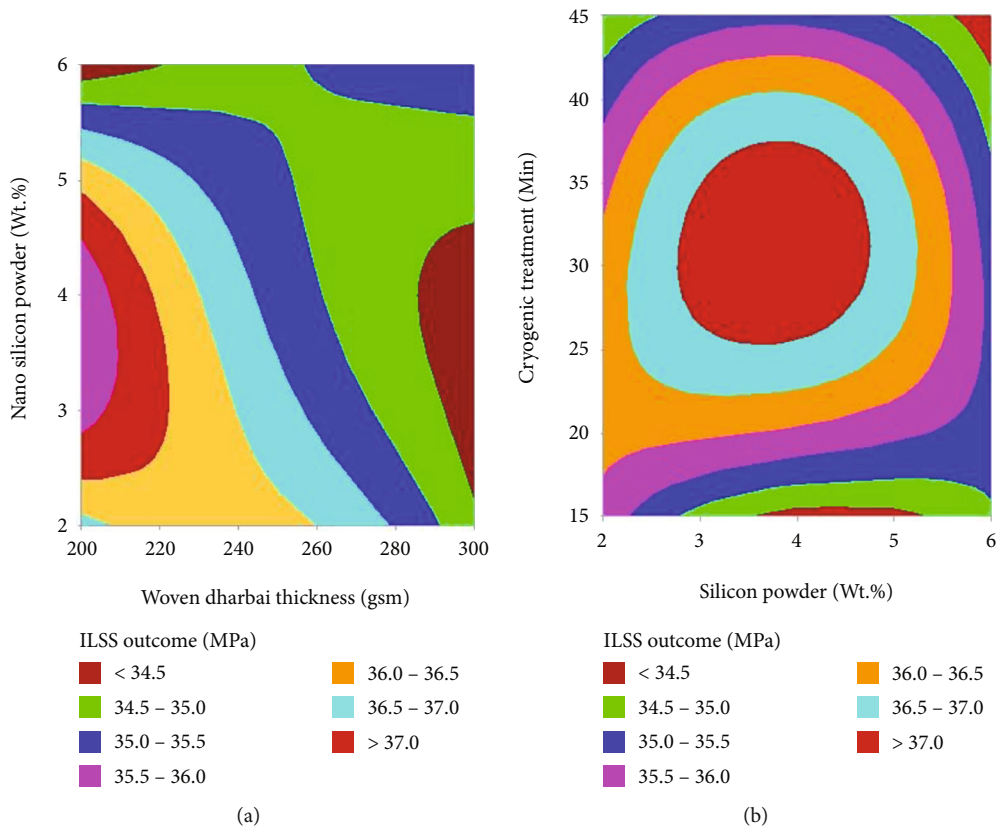


FIGURE 3: Contour plots of nanocomposites: (a) nanosilicon vs. Dharbai mat; (b) nanosilicon vs. cryogenic treatment.

the bonding between layers to resist shear pressure at a specific location [37]. Table 3 shows the average values of the S/N ratio of nanocomposites. The mean value of ILSS outcome is shown in Table 4, and the S/N values of ILSS outcome are shown in Table 5. The ILSS response of composites is used

to determine if there are shear behaviours between the layers of the material. The ILSS examination is performed on composites to determine the bonding between layers to resist shear pressure at a specified spot. The bending modulus and deformation between the plies strongly rely on the

TABLE 6: ANOVA for ILSS strength of nanocomposites.

Constraints	DOF	SOS value	Variance	Percentage of influence
Nano silicon powder (wt.%)	2	1.341	0.6703	18.30
Woven Dharbai type (gsm)	2	1.620	0.8099	22.11
Number of layers (No.)	2	4.366	2.1830	59.58
Total	6	7.327	3.6632	100

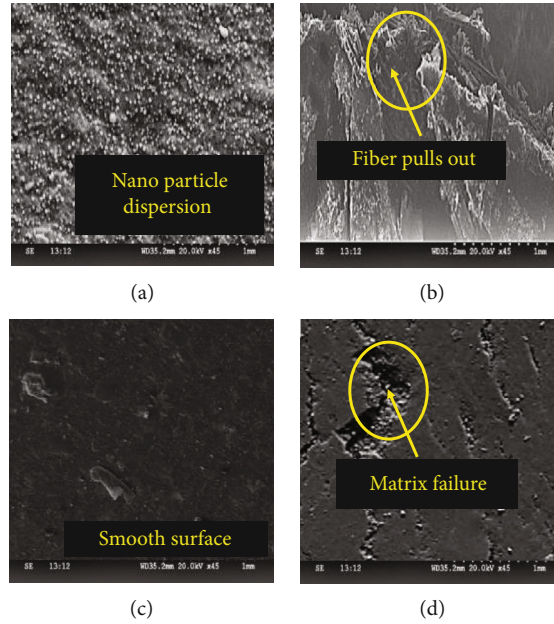


FIGURE 4: Microstructural images of nanocomposites under a cryogenic environment.

delamination between layers [38]. If the load is applied on one ply, the failure between the composite layers results in complete failure. This failure is assessed through the ILSS testing. Generally, the higher value of ILSS indicates the strong adhesions between nanofiller, epoxy matrix, and Dharbai fibres [26, 27].

Compared to the first and third levels (such as 2 and 6 wt.% silicon), the second levels (such as 4 wt.% silicon) produce the highest ILSS values in Figure 2. Increasing the nanosilicon content in composites enhances the interlaminar shear strength. However, ILSS was particularly high in 4 wt% of silicon [39]. More silicon in the matrix leads to improved matrix bonding, which results in a stronger reinforcing effect. Because of the functional groups on the nano-silicon oxide interface, the degree of cross-linking in the specimens rises, enhancing the shear behaviour. But the above results are suitable for only up to 4 wt.%. When the silicon powder increases beyond those levels, it lowers the mechanical strength [40]. This may happen due to the improper dispersion of silica particles in the epoxy matrix [41]. In the case of Dharbai fibre, all the levels provide positive effects. It demonstrates that thicker woven Dharbai (i.e., 300 gsm) would improve nanocomposite strength. It is because the presence of thicker, higher-density fibre materials reduces the impacts of voids, which is consistent with

authors Natrayan and Merneedi, Velmurugan and Kaliyamoorthy, and Islam et al.'s findings [3, 20, 25]. Cryogenic treatment of polymer-based composites is a novel method of improving mechanical characteristics. The consequence of cryogenic handling on the mechanical characteristics of polymer-based hybrid composites is depicted in Figure 2. Compared to the second and third levels (30 and 45 minutes), the first level (15 min) provides the highest mechanical strength [42]. It might be owing to the residual stress created by the compressive interface due to the cryogenic exertion of composite materials. Because of the changing matrix and fibre shrinkage, residual stresses are created at low temperatures. The interface mentioned above stresses assists in keeping fibre and matrix in contact and enhance adhesion, resulting in better outcomes. When the composites are treated beyond this limit, it can create negative effects like matrix cracking, potholing, and misalignment of fibre orientations. This may happen due to the formation of higher compressive stress at the boundary surface. Figures 3(a) and 3(b) show the contour plots of nanocomposites at various parameters.

3.3. ANOVA. The ANOVA results are utilized to determine which process characteristics influence the impacting process variables of nanosilicon and Dharbai-based hybrid

composites. The ANOVA may be written using the common outcome values. The percentage contribution through the total sum of the squared deviations may be used to assess the relevance of a processing parameter modification on concert attributes.

Table 6 shows the effect of each process parameter with nanosilica powder, woven Dharbai, and the cryogenic treatment contributing 18.30%, 22.11%, and 59.58%, respectively. This suggests that the cryogenic treatment is the most important characteristic of the silicon-based nanocomposite.

**3.4. Fractographic Analysis.** The nanocomposite morphologies at the fractured interface (following ILSS) were examined using SEM (Carl Zeiss, Supra 55). The photos support previous findings that the composites had lower permeability due to consistent fibre dispersion. The silica particles on the epoxy matrix are shown in Figure 4(a). Pull-outs of fibres and fibre packs result in the holes shown in Figure 4(b). The SEM test indicated that the matrix and reinforcement had a good connection. The resin, for example, has saturated all of the reinforcements. It is further said that the fibres in the resin system are well distributed. Figures 4(c) and 4(d) show the specimen after 30 and 45 minutes of cryogenic storage. It could be due to residual stress created by the compressive interface due to composite materials' cryogenic exertion. At low temperatures, residual stresses are formed due to changing matrix and fibre shrinkage. This interfacial stress aids in the contact and adherence of fibres and matrices, resulting in good consequences [30, 31]. The mechanical characteristics of composite specimens degraded when exposed for longer than 30 minutes. Longer cryoprocessing periods may result in higher thermal stress because of the increasing quantity of fabric mismatch. Because deformation is driven by decreasing contact, it is a far more dangerous composite structure. It might be because the time it takes to cure the epoxy resins is significantly decreased.

## 4. Conclusion

The interlaminar shear strength of silicon and Dharbai-based hybrid nanocomposites was examined in the present study, and the Taguchi technique was used to optimize the process parameters. The following findings are the results of this experimental study activity:

- (i) As per the Taguchi analysis, the suggested stages of nanosilicon filler and Dharbai-based hybrid composites are 4% weight ratios of silicon powder and 300 gsm of Dharbai fibre mat and 15 minutes of cryogenic treatment. The combinations mentioned above provide the highest strength of ILSS
- (ii) Nanoparticles and cryogenic treatments provide a high amount of residual stress in the composite interface, which helps to increase the interfacial bonding between the reinforcement and the matrix
- (iii) According to the ANOVA, the cryogenic treatment was the most significant factor, contributing up to 59.58%, followed by woven Dharbai mate, contributing 22.11%, and nanosilicon at 18.30%.
- (iv) SEM images demonstrate the interfacial bonding between the reinforcement and the epoxy matrix under cryogenic conditions

## Data Availability

The data used to support the findings of this study are included within the article. Should further data or information be required, these are available from the corresponding author upon request.

## Conflicts of Interest

The authors declare that there are no conflicts of interest regarding the publication of this paper.

## Acknowledgments

The authors thank Saveetha School of Engineering, SIMATS, Chennai, for the technical support to complete this research work. The authors appreciate the support from Ambo University, Ethiopia.

## References

- [1] I. D. G. Ary Subagia, Y. Kim, L. D. Tijing, C. S. Kim, and H. K. Shon, "Effect of stacking sequence on the flexural properties of hybrid composites reinforced with carbon and basalt fibers," *Composites. Part B, Engineering*, vol. 58, pp. 251–258, 2014.
- [2] S. D. Salman, Z. Leman, M. T. H. Sultan, M. R. Ishak, and F. Cardona, "Kenaf/synthetic and Kevlar®/cellulosic fiber-reinforced hybrid composites: a review," *BioResources*, vol. 10, no. 4, pp. 8580–8603, 2015.
- [3] L. Natrayan and A. Merneedi, "Experimental investigation on wear behaviour of bio-waste reinforced fusion fiber composite laminate under various conditions," *Materials Today: Proceedings*, vol. 37, pp. 1486–1490, 2021.
- [4] K. Renugadevi, P. K. Devan, and T. Thomas, "Fabrication of Calotropis Gigantea fibre reinforced compression spring for light weight applications," *Composites. Part B, Engineering*, vol. 172, pp. 281–289, 2019.
- [5] N. Sgriccia, M. C. Hawley, and M. Misra, "Characterization of natural fiber surfaces and natural fiber composites," *Composites. Part A, Applied Science and Manufacturing*, vol. 39, no. 10, pp. 1632–1637, 2008.
- [6] E. PREGI, G. Faludi, D. Kun, J. Móczó, and B. Pukánszky, "Three-component polypropylene/lignin/flax composites with high natural additive content for structural applications," *Industrial Crops and Products*, vol. 182, article 114890, 2022.
- [7] S. Kalyana Sundaram, S. Jayabal, N. S. Balaji, and G. Bharathiraja, "Study of chemical and mechanical properties of Dharbai fiber reinforced polyester composites," *Advanced Composite Materials*, vol. 27, no. 1, pp. 107–117, 2018.
- [8] D. Ray, B. K. Sarkar, A. K. Rana, and N. R. Bose, "Effect of alkali treated jute fibres on composite properties," *Bulletin of Materials Science*, vol. 24, no. 2, pp. 129–135, 2001.
- [9] L. Y. Mwaikambo and M. P. Ansell, "Chemical modification of hemp, sisal, jute, and kapok fibers by alkalization,"

- Journal of Applied Polymer Science*, vol. 84, no. 12, pp. 2222–2234, 2002.
- [10] V. Fiore, T. Scalici, and A. Valenza, “Effect of sodium bicarbonate treatment on mechanical properties of flax-reinforced epoxy composite materials,” *Journal of Composite Materials*, vol. 52, no. 8, pp. 1061–1072, 2018.
- [11] A. May-Pat, P. J. Valadez-González, and P. J. Herrera-Franco, “Effect of fiber surface treatments on the essential work of fracture of HDPE- continuous henequen fiber-reinforced composites,” *Polymer Testing*, vol. 32, no. 6, pp. 1114–1122, 2013.
- [12] X. Li, L. G. Tabil, and S. Panigrahi, “Chemical treatments of natural fiber for use in natural fiber-reinforced composites: a review,” *Journal of Polymers and the Environment*, vol. 15, no. 1, pp. 25–33, 2007.
- [13] G. Raghavendra, S. Ojha, S. K. Acharya, and S. K. Pal, “Influence of micro/nanofiller alumina on the mechanical behavior of novel hybrid epoxy nanocomposites,” *High Performance Polymers*, vol. 27, no. 3, pp. 342–351, 2015.
- [14] T. K. Dey, A. Hossain, M. Jamal, R. K. Layek, and M. E. Uddin, “Zinc oxide nanoparticle reinforced waste buffing dust based composite insole and its antimicrobial activity,” *Advances in Polymer Technology*, vol. 2022, 10 pages, 2022.
- [15] N. I. M. Fadilah, I. L. M. Isa, W. S. W. K. Zaman, Y. Tabata, and M. B. Fauzi, “The effect of nanoparticle-incorporated natural-based biomaterials towards cells on activated pathways: a systematic review,” *Polymers*, vol. 14, no. 3, p. 476, 2022.
- [16] S. A. Hallad, N. R. Banapurmath, V. Patil et al., “Graphene reinforced natural fiber nanocomposites for structural applications,” *IOP Conference Series: Materials Science and Engineering*, vol. 376, p. 012072, 2018.
- [17] F. Sarker, P. Potluri, S. Afroj, V. Koncherry, K. S. Novoselov, and N. Karim, “Ultrahigh performance of nanoengineered graphene-based natural jute fiber composites,” *ACS Applied Materials & Interfaces*, vol. 11, no. 23, pp. 21166–21176, 2019.
- [18] F. Perreault, A. Fonseca De Faria, and M. Elimelech, “Environmental applications of graphene-based nanomaterials,” *Chemical Society Reviews*, vol. 44, no. 16, pp. 5861–5896, 2015.
- [19] G. Velmurugan, K. Babu, L. I. Flavia, C. S. Stephy, and M. Hariharan, “Utilization of grey Taguchi method to optimize the mechanical properties of hemp and coconut shell powder hybrid composites under liquid nitrogen conditions,” *IOP Conference Series: Materials Science and Engineering*, vol. 923, no. 1, p. 012045, 2020.
- [20] V. Ganesan and B. Kaliyamoorthy, “Utilization of Taguchi technique to enhance the interlaminar shear strength of wood dust filled woven jute fiber reinforced polyester composites in cryogenic environment,” *Journal of Natural Fibers*, vol. 19, no. 6, pp. 1990–2001, 2022.
- [21] J. C. dos Santos, R. L. Siqueira, L. M. G. Vieira, R. T. S. Freire, V. Mano, and T. H. Panzera, “Effects of sodium carbonate on the performance of epoxy and polyester coir- reinforced composites,” *Polymer Testing*, vol. 67, pp. 533–544, 2018.
- [22] V. S. Nadh, C. Krishna, L. Natrayan et al., “Structural behavior of nanocoated oil palm shell as coarse aggregate in lightweight concrete,” *Journal of Nanomaterials*, vol. 2021, Article ID 4741296, 7 pages, 2021.
- [23] S. Kaliappan, M. D. Raj Kamal, S. Mohanamurugan, and P. K. Nagarajan, “Analysis of an innovative connecting rod by using finite element method,” *Taga Journal Of Graphic Technology*, vol. 14, pp. 1147–1152, 2018.
- [24] Y. Devarajan, B. Nagappan, G. Choubey, S. Vellaiyan, and K. Mehar, “Renewable pathway and twin fueling approach on ignition analysis of a dual-fuelled compression ignition engine,” *Energy & Fuels*, vol. 35, no. 12, pp. 9930–9936, 2021.
- [25] M. Saiful Islam, S. Hamdan, I. Jusoh, M. Rezaur Rahman, and A. S. Ahmed, “The effect of alkali pretreatment on mechanical and morphological properties of tropical wood polymer composites,” *Materials and Design*, vol. 33, pp. 419–424, 2012.
- [26] J. L. Tsai and M. D. Wu, “Organoclay effect on mechanical responses of glass/epoxy nanocomposites,” *Journal of Composite Materials*, vol. 42, no. 6, pp. 553–568, 2008.
- [27] K. Seeniappan, B. Venkatesan, N. N. Krishnan et al., “A comparative assessment of performance and emission characteristics of a DI diesel engine fuelled with ternary blends of two higher alcohols with lemongrass oil biodiesel and diesel fuel,” *Energy & Environment*, vol. 13, article 0958305X2110513, 2021.
- [28] G. Choubey, D. Yuvarajan, W. Huang, L. Yan, H. Babazadeh, and K. M. Pandey, “Hydrogen fuel in scramjet engines - a brief review,” *International Journal of Hydrogen Energy*, vol. 45, no. 33, pp. 16799–16815, 2020.
- [29] L. Natrayan, M. Senthil Kumar, and M. Chaudhari, “Optimization of squeeze casting process parameters to investigate the mechanical properties of AA6061/Al<sub>2</sub>O<sub>3</sub>/SiC hybrid metal matrix composites by Taguchi and Anova approach,” in *Advanced Engineering Optimization through Intelligent Techniques*, pp. 393–406, Springer, Singapore, 2020.
- [30] J. S. Raju, M. V. Depoures, J. A. Shariff, and S. U. Chakravarthy, “Characterization of natural cellulosic fibers from stem of symphirema involucratum plant,” *Journal of Natural Fibers*, vol. 2, pp. 1–16, 2021.
- [31] L. Wang, K. Wang, L. Chen, Y. Zhang, and C. He, “Preparation, morphology and thermal/mechanical properties of epoxy/nanoclay composite,” *Composites. Part A, Applied Science and Manufacturing*, vol. 37, no. 11, pp. 1890–1896, 2006.
- [32] G. Velmurugan and K. Babu, “Statistical analysis of mechanical properties of wood dust filled jute fiber based hybrid composites under cryogenic atmosphere using Grey-Taguchi method,” *Materials Research Express*, vol. 7, no. 6, 2020.
- [33] Q. Wu, H. Bai, A. Gao, and J. Zhu, “High-density grafting of carbon nanotube/carbon nanofiber hybrid on carbon fiber surface by vacuum filtration for effective interfacial reinforcement of its epoxy composites,” *Composites Science and Technology*, vol. 225, article 109522, 2022.
- [34] L. Chang and Z. Zhang, “Tribological properties of epoxy nanocomposites,” *Wear*, vol. 260, no. 7-8, pp. 869–878, 2006.
- [35] V. Balaji, S. Kaliappan, D. M. Madhuvanesan, D. S. Ezhumalai, S. Boopathi, and S. Mani, “Combustion analysis of biodiesel-powered propeller engine for least environmental concerns in aviation industry,” *Aircraft Engineering and Aerospace Technology*, vol. 94, no. 5, pp. 760–769, 2022.
- [36] Y. Devarajan, G. Choubey, and K. Mehar, “Ignition analysis on neat alcohols and biodiesel blends propelled research compression ignition engine,” *Energy Sources, Part A: Recovery, Utilization, and Environmental Effects*, vol. 42, no. 23, pp. 2911–2922, 2020.
- [37] S. Justin Abraham Baby, S. Suresh Babu, and Y. Devarajan, “Performance study of neat biodiesel-gas fuelled diesel engine,” *International Journal of Ambient Energy*, vol. 42, no. 3, pp. 269–273, 2021.



- [38] D. Veeman, M. S. Sai, P. Sureshkumar et al., "Additive manufacturing of biopolymers for tissue engineering and regenerative medicine: an overview, potential applications, advancements, and trends," *International Journal of Polymer Science*, vol. 2021, Article ID 4907027, 20 pages, 2021.
- [39] T. Ramesh, A. P. Sathiyagnanam, M. V. De Poures, and P. Murugan, "Combined effect of compression ratio and fuel injection pressure on CI engine equipped with CRDi system using *Prosopis juliflora* methyl ester/diesel blends," *International Journal of Chemical Engineering*, vol. 2022, Article ID 4617664, 12 pages, 2022.
- [40] A. S. Kaliappan, S. Mohanamurugan, and P. K. Nagarajan, "Numerical investigation of sinusoidal and trapezoidal piston profiles for an IC engine," *Journal of Applied Fluid Mechanics*, vol. 13, no. 1, pp. 287–298, 2020.
- [41] C. J. Schwartz and S. Bahadur, "Studies on the tribological behavior and transfer film-counterface bond strength for polyphenylene sulfide filled with nanoscale alumina particles," *Wear*, vol. 237, no. 2, pp. 261–273, 2000.
- [42] K. R. Sumesh, K. Kanthavel, and V. Kavimani, "Peanut oil cake-derived cellulose fiber: extraction, application of mechanical and thermal properties in pineapple/flax natural fiber composites," *International Journal of Biological Macromolecules*, vol. 150, pp. 775–785, 2020.